

Iron loss calculation in steel laminations at high frequencies

François Henrotte¹, Simon Steentjes², Christophe Geuzaine³, Kay Hameyer²

¹Institute of Mechanics Materials and Civil Engineering - UCL - Av. G. Lemaître 4-6, B-1348 Louvain-la-Neuve, Belgium

²Institute of Electrical Machines - RWTH Aachen University, D-52056 Aachen, Germany

³Dept. of Electrical Engineering and Computer Science - University of Liège, B-4000 Liège, Belgium
francois.henrotte@uclouvain.be

Abstract—The strong interaction between hysteresis and eddy currents in electrical steel laminations cannot be resolved without a strongly coupled finite element modelization. The aim of this paper is to present such a model, based on a thermodynamic analysis, together with a methodology to identify the free parameters from standard measurements (Epstein frame or Single Sheet Tester). As they fully characterize the material, irrespective of load, the identified parameters are used then to quantitatively investigate fields and losses at higher frequencies and in the presence of higher harmonics.

Index Terms—Hysteresis modeling, eddy-currents, homogenization, vector-hysteresis, higher harmonics, iron losses.

I. INTRODUCTION

Induced currents appear at various geometrical scales in ferromagnetic samples subjected to a time-varying magnetic field $\mathbf{h}(t)$. Following Bertotti [1], two main mechanisms can be distinguished. On the one hand, induced currents that result directly from the variation of the external magnetic field and loop up over paths of macroscopic dimension are called eddy currents, or Foucault currents. They depend on the geometry of the sample, and their rate of variation is directly determined by that of the applied field, $\partial_t \mathbf{h}(t)$. On the other hand, a microscopic induction mechanism also exists associated with the broken (jerky) motion of Bloch walls (Barkhausen effect) as magnetization changes in the sample. The dynamics of this motion, which is ruled by the microstructure, determines the intensity and the distribution of the microscopic induced currents, whose associated Joule losses are conventionally called hysteresis losses. The density of hysteresis losses does not depend on the geometry of the sample, neither on the rate of variation of the applied magnetic field (hysteresis is a local and quasi-static phenomenon), but it depends, at each point in the sample, on the local maxima attained by the field $\mathbf{h}(t)$ all through the magnetisation history. The term iron losses generically covers the losses associated with both phenomena.

The difficulty in modelling iron losses is associated with the fact that ferromagnetic cores generally come up as stacks of thin isolated electrical steel laminations (whose typical thickness is between 0.2 mm and 1.0 mm). Homogenization techniques have been proposed to model such composite magnetic structure [2], [3]. They however assume simplified forms for the current density across the lamination (resulting e.g. from the solution of the eddy current problem) and disregard hysteresis in general. Because a reliable mesoscopic model fails, we believe that developing homogenization techniques is premature at this stage. The interaction between hysteresis and eddy currents is indeed so strong that it cannot be resolved

without an explicit field modelization inside the laminations. The aim of this paper is to present such a strongly coupled model that addresses eddy currents (including skin effect) and hysteresis simultaneously. The proposed parametrized model is based on a thermodynamic analysis, and a methodology to identify the material parameters from standard Epstein Frame (EF) or Single Sheet Tester (SST) experiments is described. After identification, the material parameters can be exploited either to analyze the behaviour of the laminated core at higher frequencies and in the presence of higher harmonics, or to model macroscopic devices (e.g. electrical machines) by means of a homogenization approach like the one proposed in [6].

II. HYSTERESIS MATERIAL MODEL

The hysteresis model follows from the expression of the conservation of energy in the material $\dot{\Psi} = \dot{W} + \dot{Q}$, i.e. $\dot{\Psi} = \mathbf{h} \cdot \dot{\mathbf{b}} - D$ with Ψ the internal energy density and D the dissipation function. To appropriately account for the susceptibility of empty space, the induction field is written as the sum of an empty space magnetization and a material magnetization associated with the presence of microscopic moments attached to the atoms of the ferromagnetic sample, $\mathbf{b} = \mathbf{J}_0 + \mathbf{J}$. The energy density is

$$\Psi(\mathbf{J}_0, \mathbf{J}) = \frac{\mathbf{J}_0^2}{2\mu_0} + u(\mathbf{J}) \quad (1)$$

with μ_0 is the magnetic permeability of vacuum, and its variation in time writes

$$\dot{\Psi} = \frac{\mathbf{J}_0}{\mu_0} \dot{\mathbf{J}}_0 + \mathbf{h}_r \cdot \dot{\mathbf{J}} \quad \text{with} \quad \mathbf{h}_r = \partial_{\mathbf{J}} u. \quad (2)$$

The dissipation function

$$D = \chi |\dot{\mathbf{J}}| = \mathbf{h}_i \cdot \dot{\mathbf{J}} \quad \text{with} \quad \mathbf{h}_i = \partial_{\dot{\mathbf{J}}} D = \chi \frac{\dot{\mathbf{J}}}{|\dot{\mathbf{J}}|} \quad (3)$$

describes hysteresis as the magnetic analogous of a dry friction force, whose physical origin is the pinning effect that opposes the motion of Bloch walls. Conservation of energy now yields

$$(\mathbf{h} - \mathbf{J}_0/\mu_0) \cdot \dot{\mathbf{J}}_0 + (\mathbf{h} - \mathbf{h}_r - \mathbf{h}_i) \cdot \dot{\mathbf{J}} = 0 \quad \forall \dot{\mathbf{J}}_0, \dot{\mathbf{J}}. \quad (4)$$

As the state variables \mathbf{J}, \mathbf{J}_0 are arbitrary, the factors between parenthesis must vanish, and the constitutive relationships of the system are obtained, namely $\mathbf{J}_0 = \mu_0 \mathbf{h}$ and

$$\mathbf{h} - \mathbf{h}_r - \mathbf{h}_i = 0 \quad \Rightarrow \quad \mathbf{h} - \partial_{\mathbf{J}} u - \chi \frac{\dot{\mathbf{J}}}{|\dot{\mathbf{J}}|} = 0. \quad (5)$$

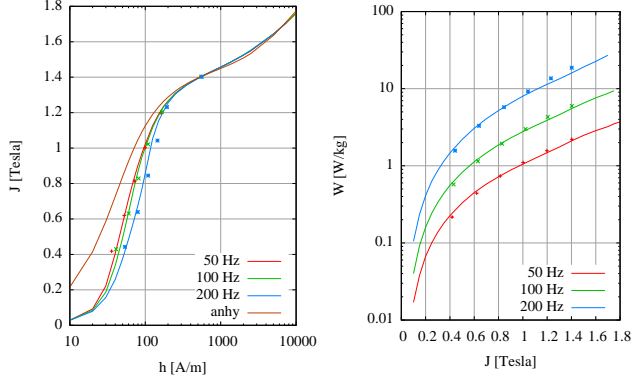


Figure 1: Comparison between measured data for M25050A FeSi non-grainoriented electrical steel at 50Hz, 100Hz and 200Hz (solid lines) and calculated data (points): Virgin and anhysteretic curve (left), iron losses (right).

In reality, the pinning strength χ is not a constant but obeys a statistical distribution, which can be represented with controllable accuracy by combining elementary models like (5) [4].

III. FINITE ELEMENT MODEL

The measured quantities in EF or SST experiments are currents and fluxes related to the magnetic field \mathbf{h} and the average induction $\langle \mathbf{b} \rangle$ across the lamination thickness. Since by construction those quantities are uniform across measured samples, it is sufficient for our purposes to work with a finite element (FE) model that consists of a 1D formulation of the eddy current problem:

$$\int_{\Omega} (\partial_t \mathbf{b} \cdot \mathbf{h}' + \sigma^{-1} \text{curl} \mathbf{h} \cdot \text{curl} \mathbf{h}') d\Omega = 0 \quad \forall \mathbf{h}' \quad (6)$$

with $\mathbf{h} = (0, h(z), 0)$. A h -field formulation is chosen because the magnetic field is the natural driving quantity for the irreversible constitutive relationship (5). Considering a lamination of thickness $2d$ with an upper surface normal vector $\mathbf{n} = (0, 0, 1)$, the domain of analysis Ω is a line parallel to \mathbf{n} , across half the thickness, and far from the edges. The boundary condition at the center of the lamination is $\text{curl} \mathbf{h}(0) \wedge \mathbf{n} = 0$, whereas a given external field $\mathbf{h}(d)$ is applied at the surface of the lamination. Iron losses per unit surface are given by the flux of the Poynting vector $\sigma^{-1} \text{curl} \mathbf{h}(d) \wedge \mathbf{h}(d)$ across the lamination surface. The details of the implementation will be given in the full paper.

IV. PARAMETER IDENTIFICATION

Standard electric steel lamination measurements are obtained under sinusoidal $\langle \mathbf{b} \rangle$ -field conditions. In order to identify them with FE simulations, the applied \mathbf{h} -field that yields a sinusoidal flux through the lamination must be determined. This can be done iteratively (See full paper). Fig. 1 shows the match obtained with a minimal number of material parameters. A very good match over a quite large range of field intensities (up to 1.4 Tesla) and frequencies (up to 200Hz) is observed. It is remarkable that the large amount of measured data can

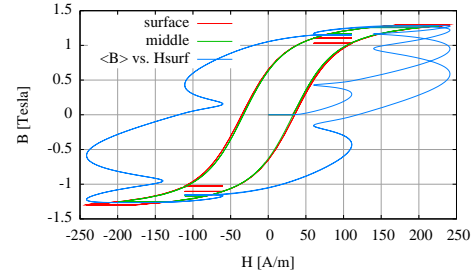


Figure 2: Comparison between the true hysteresis loops (\mathbf{h}, \mathbf{b}) at the surface and at the center of the lamination with the measured loop (\mathbf{h}, \mathbf{b}).

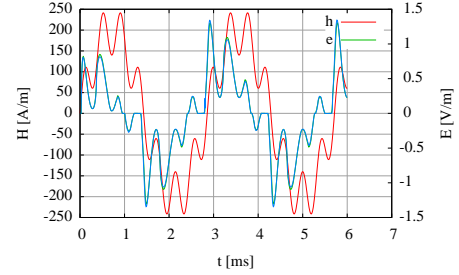


Figure 3: Time evolution of \mathbf{h} and \mathbf{e} at the surface of the lamination, the product of which is the delivered power.

be quantitatively reproduced with so few parameters (7 in this case). This indicates that the physical model based on the dry friction analogy is close enough to the reality.

V. APPLICATION

The identified parameters fully characterize the material, irrespective of load and geometry. They can be used in 2D or 3D models, or to calculate iron losses under loads for which measurements are hard to obtain or unavailable, in particular at higher frequencies and in the presence of higher harmonics. Figures 2 and 3 illustrate the rather complex phenomenology in such situations. A 350Hz magnetic field of magnitude 200A/m superimposed with a 7th higher harmonic (2450Hz) of magnitude 60A/m has been applied to the lamination model. The true and the measured hysteresis loops are compared in Fig. 2. Figure 3 shows the complex shape of the magnetic and electric fields, whose product $\mathbf{h} \wedge \mathbf{e}$ gives the iron losses.

REFERENCES

- [1] G. Bertotti, *Hysteresis in Magnetism*, Academic Press, pp. 479-503, 1998.
- [2] P. Dular, "A 3D magnetic vector potential formulation taking eddy currents in laminations into account", *IEEE Trans. on Magn.* vol. 39, pp. 1147-1150, May 2003.
- [3] L. Krähenbühl, P. Dular, T. Zeidan and F. Buret, "Homogenization of lamination stack in linear magnetodynamics", *IEEE Trans. on Magn.* 40(2) 912-915, 2004.
- [4] F. Henrotte and K. Hameyer, "A Dynamical Vector Hysteresis Model Based on an Energy Approach", *IEEE Trans. on Magn.* 43(4) 899-902, 2006.
- [5] V. François-Lavet, F. Henrotte, L. Stainier, L. Noels and C. Geuzaine, "An energy-based variational model of ferromagnetic hysteresis for finite element computations," *Journal of Computational and Applied Mathematics*, online: www.sciencedirect.com/science/article/pii/S0377042712002427.
- [6] I. Niyonzima, R. V. Sabariego, P. Dular, F. Henrotte and C. Geuzaine, "Computational homogenization for laminated ferromagnetic cores in magnetodynamics", accepted for publication in *IEEE Trans. on Magnetics*.